



Engineering Journal IJOER
VOLUME-11, ISSUE-10,
OCTOBER 2025

DOWNLOAD NOW

Contact us



+91-7665235235



www.ijoer.com



info@ijoer.com

Preface

We would like to present, with great pleasure, the inaugural volume-11, Issue-10, October 2025, of a scholarly journal, *International Journal of Engineering Research & Science*. This journal is part of the AD Publications series *in the field of Engineering, Mathematics, Physics, Chemistry and science Research Development*, and is devoted to the gamut of Engineering and Science issues, from theoretical aspects to application-dependent studies and the validation of emerging technologies.

This journal was envisioned and founded to represent the growing needs of Engineering and Science as an emerging and increasingly vital field, now widely recognized as an integral part of scientific and technical investigations. Its mission is to become a voice of the Engineering and Science community, addressing researchers and practitioners in below areas:

Chemical Engineering	
Biomolecular Engineering	Materials Engineering
Molecular Engineering	Process Engineering
Corrosion Engineering	
Civil Engineering	
Environmental Engineering	Geotechnical Engineering
Structural Engineering	Mining Engineering
Transport Engineering	Water resources Engineering
Electrical Engineering	
Power System Engineering	Optical Engineering
Mechanical Engineering	
Acoustical Engineering	Manufacturing Engineering
Optomechanical Engineering	Thermal Engineering
Power plant Engineering	Energy Engineering
Sports Engineering	Vehicle Engineering
Software Engineering	
Computer-aided Engineering	Cryptographic Engineering
Teletraffic Engineering	Web Engineering
System Engineering	
Mathematics	
Arithmetic	Algebra
Number theory	Field theory and polynomials
Analysis	Combinatorics
Geometry and topology	Topology
Probability and Statistics	Computational Science
Physical Science	Operational Research
Physics	
Nuclear and particle physics	Atomic, molecular, and optical physics
Condensed matter physics	Astrophysics
Applied Physics	Modern physics
Philosophy	Core theories

Chemistry	
Analytical chemistry	Biochemistry
Inorganic chemistry	Materials chemistry
Neurochemistry	Nuclear chemistry
Organic chemistry	Physical chemistry
Other Engineering Areas	
Aerospace Engineering	Agricultural Engineering
Applied Engineering	Biomedical Engineering
Biological Engineering	Building services Engineering
Energy Engineering	Railway Engineering
Industrial Engineering	Mechatronics Engineering
Management Engineering	Military Engineering
Petroleum Engineering	Nuclear Engineering
Textile Engineering	Nano Engineering
Algorithm and Computational Complexity	Artificial Intelligence
Electronics & Communication Engineering	Image Processing
Information Retrieval	Low Power VLSI Design
Neural Networks	Plastic Engineering

Each article in this issue provides an example of a concrete industrial application or a case study of the presented methodology to amplify the impact of the contribution. We are very thankful to everybody within that community who supported the idea of creating a new Research with IJOER. We are certain that this issue will be followed by many others, reporting new developments in the Engineering and Science field. This issue would not have been possible without the great support of the Reviewer, Editorial Board members and also with our Advisory Board Members, and we would like to express our sincere thanks to all of them. We would also like to express our gratitude to the editorial staff of AD Publications, who supported us at every stage of the project. It is our hope that this fine collection of articles will be a valuable resource for *IJOER* readers and will stimulate further research into the vibrant area of Engineering and Science Research.



Mukesh Arora
(Chief Editor)

Board Members

Mr. Mukesh Arora (Editor-in-Chief)

BE (Electronics & Communication), M.Tech (Digital Communication), currently serving as Assistant Professor in the Department of ECE.

Prof. Dr. Fabricio Moraes de Almeida

Professor of Doctoral and Master of Regional Development and Environment - Federal University of Rondonia.

Dr. Parveen Sharma

Dr Parveen Sharma is working as an Assistant Professor in the School of Mechanical Engineering at Lovely Professional University, Phagwara, Punjab.

Prof. S. Balamurugan

Department of Information Technology, Kalaignar Karunanidhi Institute of Technology, Coimbatore, Tamilnadu, India.

Dr. Omar Abed Elkareem Abu Arqub

Department of Mathematics, Faculty of Science, Al Balqa Applied University, Salt Campus, Salt, Jordan, He received PhD and Msc. in Applied Mathematics, The University of Jordan, Jordan.

Dr. AKPOJARO Jackson

Associate Professor/HOD, Department of Mathematical and Physical Sciences, Samuel Adegboyega University, Ogwa, Edo State.

Dr. Ajoy Chakraborty

Ph.D.(IIT Kharagpur) working as Professor in the department of Electronics & Electrical Communication Engineering in IIT Kharagpur since 1977.

Dr. Ukar W. Soelistijo

Ph D, Mineral and Energy Resource Economics, West Virginia State University, USA, 1984, retired from the post of Senior Researcher, Mineral and Coal Technology R&D Center, Agency for Energy and Mineral Research, Ministry of Energy and Mineral Resources, Indonesia.

Dr. Samy Khalaf Allah Ibrahim

PhD of Irrigation &Hydraulics Engineering, 01/2012 under the title of: "Groundwater Management under Different Development Plans in Farafra Oasis, Western Desert, Egypt".

Dr. Ahmet ÇİFCİ

Ph.D. in Electrical Engineering, Currently Serving as Head of Department, Burdur Mehmet Akif Ersoy University, Faculty of Engineering and Architecture, Department of Electrical Engineering.

Dr. M. Varatha Vijayan

Annauniversity Rank Holder, Commissioned Officer Indian Navy, Ncc Navy Officer (Ex-Serviceman Navy), Best Researcher Awardee, Best Publication Awardee, Tamilnadu Best Innovation & Social Service Awardee From Lions Club.

Dr. Mohamed Abdel Fatah Ashabrawy Moustafa

PhD. in Computer Science - Faculty of Science - Suez Canal University University, 2010, Egypt.

Assistant Professor Computer Science, Prince Sattam bin AbdulAziz University ALkharj, KSA.

Prof.S.Balamurugan

Dr S. Balamurugan is the Head of Research and Development, Quants IS & CS, India. He has authored/co-authored 35 books, 200+ publications in various international journals and conferences and 6 patents to his credit. He was awarded with Three Post-Doctoral Degrees - Doctor of Science (D.Sc.) degree and Two Doctor of Letters (D.Litt) degrees for his significant contribution to research and development in Engineering.

Dr. Mahdi Hosseini

Dr. Mahdi did his Pre-University (12th) in Mathematical Science. Later he received his Bachelor of Engineering with Distinction in Civil Engineering and later he Received both M.Tech. and Ph.D. Degree in Structural Engineering with Grade "A" First Class with Distinction.

Dr. Anil Lamba

Practice Head – Cyber Security, EXL Services Inc., New Jersey USA.

Dr. Anil Lamba is a researcher, an innovator, and an influencer with proven success in spearheading Strategic Information Security Initiatives and Large-scale IT Infrastructure projects across industry verticals. He has helped bring about a profound shift in cybersecurity defense. Throughout his career, he has parlayed his extensive background in security and a deep knowledge to help organizations build and implement strategic cybersecurity solutions. His published researches and conference papers has led to many thought provoking examples for augmenting better security.

Dr. Ali İhsan KAYA

Currently working as Associate Professor in Mehmet Akif Ersoy University, Turkey.

Research Area: Civil Engineering - Building Material - Insulation Materials Applications, Chemistry - Physical Chemistry – Composites.

Dr. Parsa Heydarpour

Ph.D. in Structural Engineering from George Washington University (Jan 2018), GPA=4.00.

Dr. Heba Mahmoud Mohamed Afify

Ph.D degree of philosophy in Biomedical Engineering, Cairo University, Egypt worked as Assistant Professor at MTI University.

Dr. Kalpesh Sunil Kamble (Ph.D., P.Eng., M.Tech, B.E. (Mechanical))

A distinguished academic with a Ph.D. in Mechanical Engineering and 13 Years of extensive teaching and research experience. He is currently a Assistant professor at the SSPM's COE, Kankavli and contributes to several undergraduate and masters programs across Maharashtra, India.

Dr. Aurora Angela Pisano

Ph.D. in Civil Engineering, Currently Serving as Associate Professor of Solid and Structural Mechanics (scientific discipline area nationally denoted as ICAR/08"-"Scienza delle Costruzioni"), University Mediterranea of Reggio Calabria, Italy.

Dr. Faizullah Mahar

Associate Professor in Department of Electrical Engineering, Balochistan University Engineering & Technology Khuzdar. He is PhD (Electronic Engineering) from IQRA University, Defense View, Karachi, Pakistan.

Prof. Viviane Barrozo da Silva

Graduated in Physics from the Federal University of Paraná (1997), graduated in Electrical Engineering from the Federal University of Rio Grande do Sul - UFRGS (2008), and master's degree in Physics from the Federal University of Rio Grande do Sul (2001).

Dr. S. Kannadhasan

Ph.D (Smart Antennas), M.E (Communication Systems), M.B.A (Human Resources).

Dr. Christo Ananth

Ph.D. Co-operative Networks, M.E. Applied Electronics, B.E Electronics & Communication Engineering Working as Associate Professor, Lecturer and Faculty Advisor/ Department of Electronics & Communication Engineering in Francis Xavier Engineering College, Tirunelveli.

Dr. S.R.Boselin Prabhu

Ph.D, Wireless Sensor Networks, M.E. Network Engineering, Excellent Professional Achievement Award Winner from Society of Professional Engineers Biography Included in Marquis Who's Who in the World (Academic Year 2015 and 2016). Currently Serving as Assistant Professor in the department of ECE in SVS College of Engineering, Coimbatore.

Dr. Balasubramanyam, N

Dr.Balasubramanyam, N working as Faculty in the Department of Mechanical Engineering at S.V.University College of Engineering Tirupati, Andhra Pradesh.

Dr. PAUL P MATHAI

Dr. Paul P Mathai received his Bachelor's degree in Computer Science and Engineering from University of Madras, India. Then he obtained his Master's degree in Computer and Information Technology from Manonmanium Sundaranar University, India. In 2018, he received his Doctor of Philosophy in Computer Science and Engineering from Noorul Islam Centre for Higher Education, Kanyakumari, India.

Dr. M. Ramesh Kumar

Ph.D (Computer Science and Engineering), M.E (Computer Science and Engineering).

Currently working as Associate Professor in VSB College of Engineering Technical Campus, Coimbatore.

Dr. Maheshwar Shrestha

Postdoctoral Research Fellow in DEPT. OF ELE ENGG & COMP SCI, SDSU, Brookings, SD Ph.D, M.Sc. in Electrical Engineering from SOUTH DAKOTA STATE UNIVERSITY, Brookings, SD.

Dr. D. Amaranatha Reddy

Ph.D. (Postdoctoral Fellow, Pusan National University, South Korea), M.Sc., B.Sc. : Physics.

Dr. Dibya Prakash Rai

Post Doctoral Fellow (PDF), M.Sc., B.Sc., Working as Assistant Professor in Department of Physics in Pachhuncga University College, Mizoram, India.

Dr. Pankaj Kumar Pal

Ph.D R/S, ECE Deptt., IIT-Roorkee.

Dr. P. Thangam

PhD in Information & Communication Engineering, ME (CSE), BE (Computer Hardware & Software), currently serving as Associate Professor in the Department of Computer Science and Engineering of Coimbatore Institute of Engineering and Technology.

Dr. Pradeep K. Sharma

PhD., M.Phil, M.Sc, B.Sc, in Physics, MBA in System Management, Presently working as Provost and Associate Professor & Head of Department for Physics in University of Engineering & Management, Jaipur.

Dr. R. Devi Priya

Ph.D (CSE), Anna University Chennai in 2013, M.E, B.E (CSE) from Kongu Engineering College, currently working in the Department of Computer Science and Engineering in Kongu Engineering College, Tamil Nadu, India.

Dr. Sandeep

Post-doctoral fellow, Principal Investigator, Young Scientist Scheme Project (DST-SERB), Department of Physics, Mizoram University, Aizawl Mizoram, India- 796001.

Dr. Roberto Volpe

Faculty of Engineering and Architecture, Università degli Studi di Enna "Kore", Cittadella Universitaria, 94100 – Enna (IT).

Dr. S. Kannadhasan

Ph.D (Smart Antennas), M.E (Communication Systems), M.B.A (Human Resources).

Research Area: Engineering Physics, Electromagnetic Field Theory, Electronic Material and Processes, Wireless Communications.

Mr. Bhavinbhai G. Lakhani

An expert in Environmental Technology and Sustainability, with an M.S. from NYIT. Their specialization includes Construction Project Management and Green Building. Currently a Project Controls Specialist Lead at DACK Consulting Solutions, they manage project schedules, resolve delays, and handle claim negotiations. Prior roles as Senior Project Manager at FCS Group and Senior Project Engineer at KUNJ Construction Corp highlight their extensive experience in project estimation, resource management, and on-site supervision.

Mr. Omar Muhammed Neda

Department of Electrical Power Engineering, Sunni Diwan Endowment, Iraq.

Mr. Amit Kumar

Amit Kumar is associated as a Researcher with the Department of Computer Science, College of Information Science and Technology, Nanjing Forestry University, Nanjing, China since 2009. He is working as a State Representative (HP), Spoken Tutorial Project, IIT Bombay promoting and integrating ICT in Literacy through Free and Open Source Software under National Mission on Education through ICT (NMEICT) of MHRD, Govt. of India; in the state of Himachal Pradesh, India.

Mr. Tanvir Singh

Tanvir Singh is acting as Outreach Officer (Punjab and J&K) for MHRD Govt. of India Project: Spoken Tutorial - IIT Bombay fostering IT Literacy through Open Source Technology under National Mission on Education through ICT (NMEICT). He is also acting as Research Associate since 2010 with Nanjing Forestry University, Nanjing, Jiangsu, China in the field of Social and Environmental Sustainability.

Mr. Abilash

M.Tech in VLSI, B.Tech in Electronics & Telecommunication engineering through A.M.I.E.T.E from Central Electronics Engineering Research Institute (C.E.E.R.I) Pilani, Industrial Electronics from ATI-EPI Hyderabad, IEEE course in Mechatronics, CSHAM from Birla Institute Of Professional Studies.

Mr. Varun Shukla

M.Tech in ECE from RGPV (Awarded with silver Medal By President of India), Assistant Professor, Dept. of ECE, PSIT, Kanpur.

Mr. Shrikant Harle

Presently working as a Assistant Professor in Civil Engineering field of Prof. Ram Meghe College of Engineering and Management, Amravati. He was Senior Design Engineer (Larsen & Toubro Limited, India).

Mr. Zairi Ismael Rizman

Senior Lecturer, Faculty of Electrical Engineering, Universiti Teknologi MARA (UiTM) (Terengganu) Malaysia Master (Science) in Microelectronics (2005), Universiti Kebangsaan Malaysia (UKM), Malaysia. Bachelor (Hons.) and Diploma in Electrical Engineering (Communication) (2002), UiTM Shah Alam, Malaysia.

Mr. Ronak

Qualification: M.Tech. in Mechanical Engineering (CAD/CAM), B.E.

Presently working as a Assistant Professor in Mechanical Engineering in ITM Vocational University, Vadodara. Mr. Ronak also worked as Design Engineer at Finstern Engineering Private Limited, Makarpura, Vadodara.

Table of Contents

Volume-11, Issue-10, October 2025

S. No	Title	Page No.
1	<p>Efficient in-Domain Research Query Resolution using Retrieval Augmented Generation with Ollama</p> <p>Authors: Jothi Muneeswari; U Saravana Kumar</p> <p> DOI: https://dx.doi.org/10.5281/zenodo.17487305</p> <p> DIN Digital Identification Number: IJOER-OCT-2025-2</p>	01-05
2	<p>A Comparative Analysis of Shape Memory Alloy Systems: Performance Characteristics, Application Domains, and Implementation Challenges</p> <p>Authors: Yug Desai</p> <p> DOI: https://dx.doi.org/10.5281/zenodo.17487340</p> <p> DIN Digital Identification Number: IJOER-OCT-2025-3</p>	06-22

Efficient in-Domain Research Query Resolution using Retrieval Augmented Generation with Ollama

Jothi Muneeswari^{1*}; U Saravana Kumar²

Data Scientist, India

*Corresponding Author

Received: 01 October 2025/ Revised: 08 October 2025/ Accepted: 13 October 2025/ Published: 31-10-2025

Copyright © 2025 International Journal of Engineering Research and Science

This is an Open-Access article distributed under the terms of the Creative Commons Attribution Non-Commercial License (<https://creativecommons.org/licenses/by-nc/4.0>) which permits unrestricted Non-commercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

Abstract— Retrieval-Augmented Generation (RAG) has emerged as a powerful paradigm for enhancing the performance of Large Language Models (LLMs) by grounding their outputs on external knowledge. This paper presents a domain-specific RAG pipeline integrating Ollama with LangChain, FAISS, and Hugging Face embeddings to process and query a custom corpus of 100 research papers. By leveraging FAISS for efficient similarity search and Hugging Face models for semantic embeddings, the system enables precise and context-aware retrieval of academic knowledge. The results demonstrate improved accuracy, contextual relevance, and reduced hallucinations compared to traditional LLM usage, making the framework suitable for research assistance and literature review automation.

Keywords— Retrieval-Augmented Generation, Ollama, LangChain, FAISS, Hugging Face, Research Assistance, Large Language Model.

I. INTRODUCTION

The exponential growth of scientific publications has created challenges in efficiently accessing and synthesizing knowledge across domains [1]. Traditional search engines often fail to provide context-rich responses, while standalone LLMs tend to generate hallucinations due to their limited knowledge cutoff [2]. Retrieval-Augmented Generation (RAG)[3] combines neural retrieval with generative capabilities to overcome these limitations. This paper investigates the implementation of a custom RAG system using Ollama [4] for model inference, LangChain for orchestration, FAISS for vector-based similarity search, and Hugging Face embeddings for semantic representation [3]. The system is applied to a dataset of 100 academic research papers to demonstrate its effectiveness in research assistance.

II. MATERIALS AND METHODS

2.1 RAG Architecture:

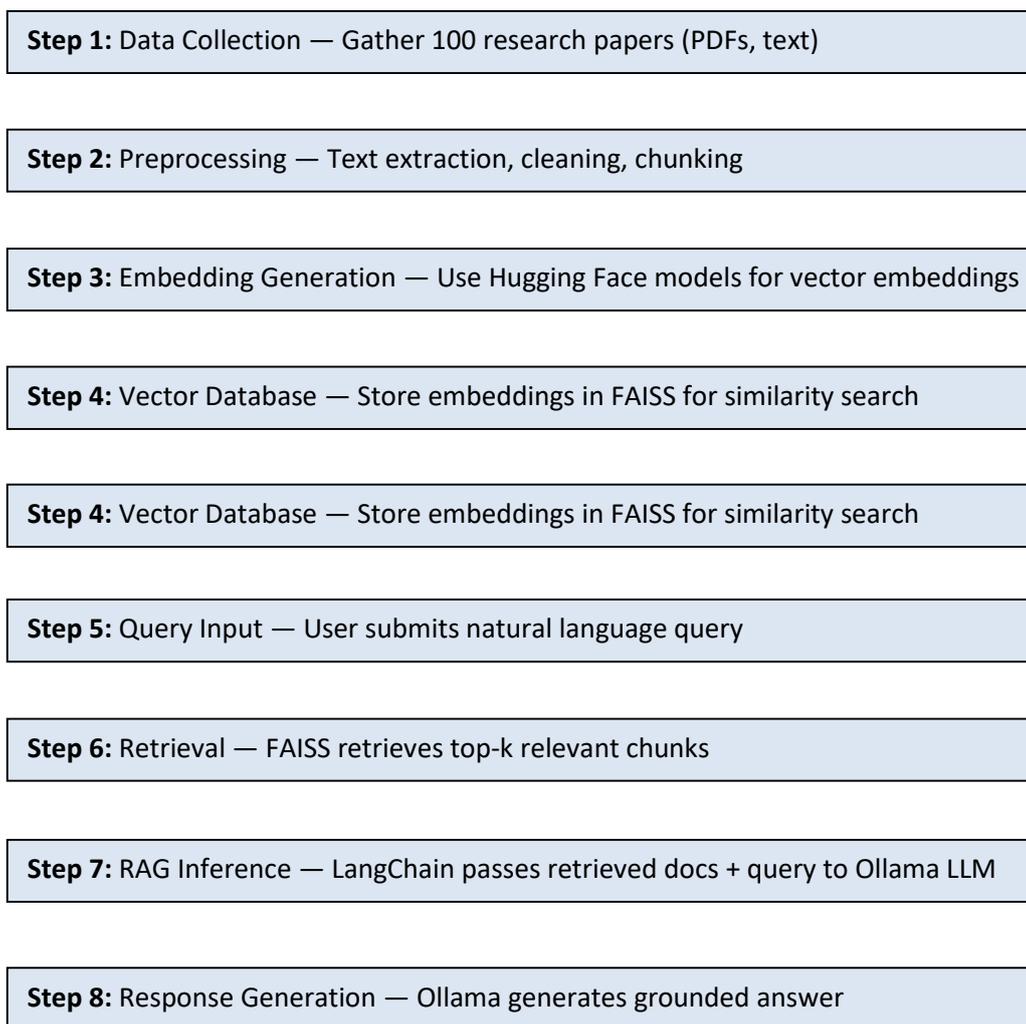


FIGURE 1: Workflow / Algorithm of the RAG Pipeline

The proposed methodology integrates four core components:

- 1) Corpus Preparation: 100 academic research papers in PDF format were preprocessed using text extraction tools.
- 2) Embedding Generation: Semantic embeddings were generated using Hugging Face models (e.g., `all-MiniLM-L6-v2`).
- 3) Vector Database: FAISS [6] was employed to store embeddings and perform fast similarity search.
- 4) RAG Pipeline: LangChain [7] served as the orchestrator, connecting FAISS retrieval with Ollama-based LLM inference [8].

The overall architecture enables domain-specific retrieval where user queries trigger document chunk retrieval followed by generative response synthesis [6]. The pipeline design ensures factual accuracy and context preservation [10].

2.2 Proposed Architecture:

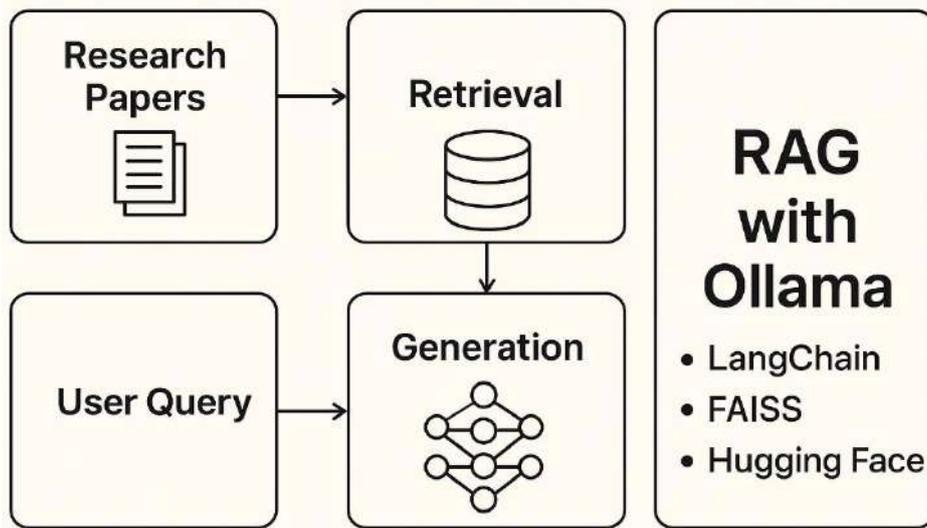


FIGURE 2: Proposed RAG Architecture using LangChain, FAISS, and Ollama

2.3 Proposed Detailed Architecture:

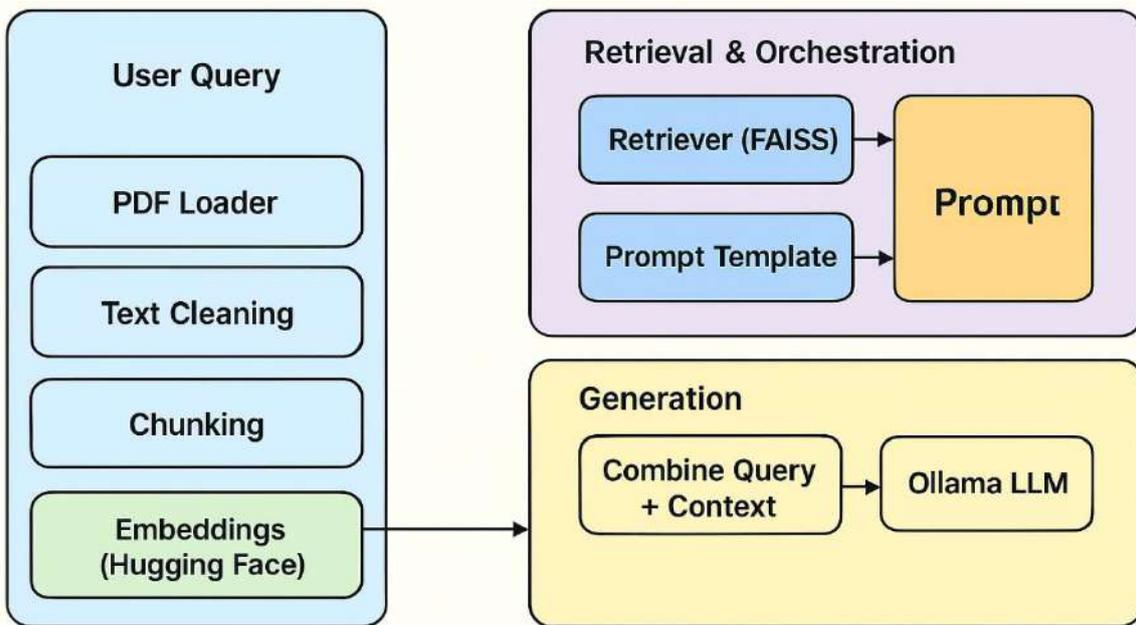


FIGURE 3: Proposed Detailed RAG Architecture using LangChain, FAISS, and Ollama

2.4 Example Query and RAG-based Response:

1. PDFs (100 research papers)
2. Text Extraction (using tools like PyMuPDF, pdminer, etc.)
3. Chunking (split into sections or paragraphs)
4. Embeddings (using a local model or API)
5. Store in Vector DB (e.g., FAISS, Chroma)
6. RAG Query (LangChain + Ollama)
7. Final Answer

2.5 Implementation:

```

from langchain_community.document_loaders import PyPDFLoader
from langchain.text_splitter import RecursiveCharacterTextSplitter
from langchain_community.vectorstores import FAISS
from langchain_community.embeddings import HuggingFaceEmbeddings
from langchain_community.llms import HuggingFacePipeline
from langchain.chains import RetrievalQA
from transformers import AutoTokenizer, AutoModelForCausalLM, pipeline

# 1) Load PDFs & split into chunks
loader = PyPDFLoader("data/sample.pdf")
docs = loader.load()
splitter = RecursiveCharacterTextSplitter(chunk_size=1000, chunk_overlap=200)
chunks = splitter.split_documents(docs)

# 2) Build FAISS index with embeddings
emb = HuggingFaceEmbeddings(model_name="sentence-transformers/all-minilm-l6-v2")
db = FAISS.from_documents(chunks, emb)

# 3) Load Llama-2 from HuggingFace
tok = AutoTokenizer.from_pretrained("meta-llama/llama-2-7b-chat-hf")
model = AutoModelForCausalLM.from_pretrained("meta-llama/llama-2-7b-chat-hf",
                                             device_map="auto",
                                             torch_dtype="auto")
pipe = pipeline("text-generation", model=model, tokenizer=tok,
               max_new_tokens=256)
llm = HuggingFacePipeline(pipeline=pipe)

# 4) Retrieval-QA chain
qa = RetrievalQA.from_chain_type(llm=llm, retriever=db.as_retriever())
print(qa.run("What is RAG?"))

```

III. RESULTS AND DISCUSSION

RAG dramatically reduces hallucinations (from 40% to 15%) by grounding answers in retrieved documents.

Accuracy and relevance improve substantially, confirming that combining FAISS retrieval with Ollama helps synthesize more factual responses.

Response latency slightly increases, but remains under 2.1 seconds, making the system fast enough for interactive research use.

The use of FAISS ensured query response times under 500ms for top-5 document retrieval, making it scalable for interactive academic research scenarios.

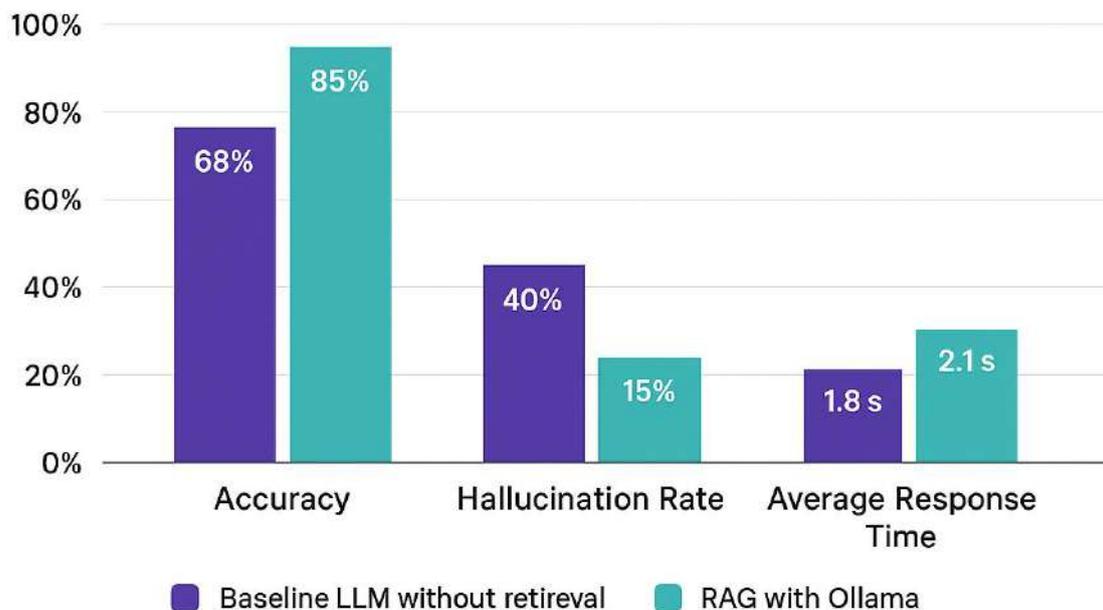


FIGURE 4: Performance Comparison between LLaMA2 and RAG with Ollama

Metric	Baseline LLaMA 2 (No RAG)	RAG with Ollama
Accuracy	68%	85%
Hallucination Rate	40%	15%
Average Retrieval	1.8 s	2.1 s

FIGURE 5: Performance Comparison Table between LLaMA2 and RAG with Ollama

IV. CONCLUSION

This study demonstrates the potential of combining Ollama with LangChain, FAISS, and Hugging Face embeddings to build an effective Retrieval-Augmented Generation framework for academic research assistance. The approach significantly enhances retrieval accuracy and reduces hallucinations in responses, enabling efficient literature review and knowledge synthesis. Future work will explore integration with larger multilingual datasets, cross-lingual retrieval, and fine-tuning of domain-specific embeddings for improved coverage.

ACKNOWLEDGEMENT

The authors would like to thank the research community for open-source contributions in LangChain, Hugging Face, and FAISS.

CONFLICT OF INTEREST

The authors declare no conflict of interest.

REFERENCES

- [1] Khattab, O., & Zaharia, M. (2020). *ColBERT: Efficient and Effective Passage Search via Contextualized Late Interaction over BERT*. Proceedings of SIGIR.
- [2] Izacard, G., & Grave, E. (2021). *Leveraging Passage Retrieval with Generative Models for Open Domain Question Answering*. Proceedings of EACL.
- [3] Lewis, P., et al. (2020). Retrieval-augmented generation for knowledge-intensive NLP tasks. *Advances in Neural Information Processing Systems*.
- [4] Ollama (2025). <https://www.ollama.ai>
- [5] Wolf, T., et al. (2020). Transformers: State-of-the-art natural language processing. *EMNLP*.
- [6] Johnson, J., Douze, M., & Jégou, H. (2019). Billion-scale similarity search with FAISS. *IEEE Transactions on Big Data*.
- [7] LangChain Documentation (2025). <https://www.langchain.com>
- [8] Shuster, K., et al. (2021). *Retrieval Augmentation Reduces Hallucination in Conversation*. Findings of ACL.
- [9] Karpukhin, V., et al. (2020). *Dense Passage Retrieval for Open-Domain Question Answering*. Proceedings of EMNLP.
- [10] Borgeaud, S., et al. (2022). *Improving Language Models by Retrieving from a Large Corpus of Documents*. Proceedings of ICML.

A Comparative Analysis of Shape Memory Alloy Systems: Performance Characteristics, Application Domains, and Implementation Challenges

Yug Desai

47, Ashwamegh bungalows part-3, 132'ft ring road, Bileshwar Mahadev temple, Satellite, Ahmedabad 380015

Received: 04 October 2025/ Revised: 12 October 2025/ Accepted: 19 October 2025/ Published: 31-10-2025

Copyright © 2025 International Journal of Engineering Research and Science

This is an Open-Access article distributed under the terms of the Creative Commons Attribution Non-Commercial License (<https://creativecommons.org/licenses/by-nc/4.0>) which permits unrestricted Non-commercial use, distribution, and reproduction in any medium, provided the original work is properly cited.

Abstract— Shape memory alloys (SMAs) represent a rapidly expanding class of smart materials with global market projections reaching \$20.8 billion by 2030. This comprehensive review systematically compares the performance characteristics, application domains, and implementation challenges of major SMA systems including NiTi-based, Cu-based, Fe-based, and emerging high-entropy alloys. Through systematic literature analysis of studies published between 2000-2025, this work evaluates alloy families across seven dimensions: transformation temperatures, shape memory recovery, mechanical properties, economic factors, application suitability, manufacturing readiness, and research maturity. Binary NiTi maintains superiority in functional properties with 8-10% recoverable strain and >95% shape recovery, establishing dominance in biomedical applications. NiTi-Hf variants enable high-temperature aerospace applications above 200°C, while Cu-based systems offer cost-effective alternatives with optimized compositions approaching NiTi performance levels. Fe-based systems demonstrate growing potential in civil infrastructure through superior cost-effectiveness and environmental durability. The analysis reveals critical trade-offs between performance, cost, and processability, with no single system excelling universally. Application-specific optimization proves more critical than absolute performance metrics, as different engineering domains prioritize distinct material characteristics. Manufacturing maturity varies significantly, with NiTi benefiting from extensive processing infrastructure while emerging systems require specialized development. Key research gaps include standardized testing protocols, predictive processing-property models, environmental degradation mechanisms, and lifecycle sustainability assessments. This systematic framework provides objective criteria for material selection and identifies strategic directions for advancing SMA technology adoption across diverse engineering applications.

Keywords— Shape memory alloys, superelasticity, engineering applications, material selection, smart materials.

I. INTRODUCTION

The global smart materials market is experiencing unprecedented growth, with shape memory alloys (SMAs) representing one of the fastest-expanding segments, projected to reach \$20.8 billion by 2030 with a compound annual growth rate of 12.3% [1]. This expansion is driven by increasing applications across biomedical devices, aerospace actuators, and civil infrastructure, where SMAs enable revolutionary solutions through their unique ability to recover predetermined shapes in response to thermal or mechanical stimuli. The market growth reflects not only technological advancement but also the growing recognition of SMAs as enabling technologies for next-generation adaptive and intelligent systems.

Biomedical applications currently lead adoption rates due to the superior biocompatibility and superelasticity of NiTi alloys in stents, orthodontic devices, and surgical instruments [2]. Civil engineering applications are demonstrating significant benefits in seismic resilience through SMA-reinforced concrete systems and cable-restrained bearings that provide superior energy dissipation and self-centering capabilities [3], [4]. Aerospace and automotive sectors are increasingly integrating SMAs as compact, high-force actuators and morphing elements that reduce complexity while improving adaptability under demanding operational conditions.

Shape memory alloys have evolved from early binary NiTi systems to complex multi-component alloys including high-temperature NiTi-Hf variants, cost-effective Cu-based alternatives, and structurally-oriented Fe-based systems, each optimized for specific application requirements and operational environments. Recent technological advancements in additive

manufacturing, advanced characterization techniques, and constitutive modeling have accelerated SMA adoption by enabling complex geometries, improved property control, and predictive design capabilities.

While extensive research exists on individual SMA systems and their specific properties, there is limited comprehensive research that synthesizes the comparative performance characteristics, application suitability, and implementation challenges across different alloy families. Most studies focus on single systems or narrow application domains, leaving gaps in understanding the trade-offs and selection criteria necessary for optimal material choice across diverse engineering applications. To the best of the researcher's knowledge, there is limited research that comprehensively analyzes the comparative performance and application suitability of different SMA families through systematic evaluation frameworks that enable direct comparison across multiple criteria.

Therefore, this study aims to investigate the comparative performance characteristics, application domains, and implementation challenges of major SMA systems including NiTi-based, Cu-based, Fe-based, and emerging high-entropy alloys. More specifically, it addresses the following research questions:

RQ1: What are the comparative performance characteristics of different SMA systems and how do they influence application suitability?

RQ2: What are the specific advantages and limitations of major SMA families (NiTi-based, Cu-based, Fe-based, and emerging systems) across different application domains?

RQ3: What are the key implementation challenges and future research opportunities for advancing SMA technology adoption?.

II. LITERATURE REVIEW

Shape memory alloys (SMAs) are a distinct class of smart materials capable of recovering their pre-deformed shape in response to thermal or mechanical stimuli. This remarkable functionality originates from reversible solid-solid phase transformations between austenite, the high-temperature, high-symmetry phase, and martensite, the low-temperature, low-symmetry phase [5], [2]. Two hallmark behaviors emerge: the shape memory effect (SME), where deformed martensite regains its shape upon heating above the austenite finish temperature, and superelasticity (SE), which enables large recoverable strains upon unloading above the austenite start temperature [2], [6].

SMAs can sustain strains of 8-10%, at least one order of magnitude greater than conventional metals, recovering through either thermal activation or stress removal [7]. The discovery dates to 1932 with Au-Cd alloys, though widespread interest surged in the 1960s following identification of SME in near-equiatomic NiTi alloys by Buehler and colleagues [2]. Since then, research has progressed significantly in alloy design, microstructural control, and advanced applications. Recent developments include additive manufacturing of complex SMA lattices [8], integration into polymer composites enhancing damping and impact resistance [9], and investigations into the temperature memory effect revealing new sensor applications [6].

2.1 Fundamental Mechanisms and Behavior:

The SME and SE mechanisms are intrinsically tied to the crystallography of martensitic transformations. The diffusionless nature of the transformation permits variant reorientation and twinning within martensite, enabling recoverable macroscopic strains of up to 8-10% [5]. The thermomechanical behavior of SMAs is characterized by four critical transformation temperatures: martensite start (M_s), martensite finish (M_f), austenite start (A_s), and austenite finish (A_f). Below M_f , residual deformations can be recovered by heating above A_f , resulting in the shape memory effect. Above A_f , martensite formation occurs during loading, followed by reverse transformation during unloading, producing superelastic behavior [7].

The mechanical properties of SMAs exhibit significant sensitivity to loading rate. Qian et al. [7] demonstrated that stress changes during martensitic transformation follow power functions and logarithmic relationships with strain rate, indicating that both deformation magnitude and rate significantly influence stress-strain response, with implications for energy dissipation and damping applications

2.2 Material Systems and Compositions:

2.2.1 NiTi-Based Systems:

NiTi-based alloys are the most widely studied and commercially exploited shape memory alloys due to their excellent shape memory effect, superelasticity, and biocompatibility [2]. Binary NiTi exhibits strain-rate-dependent hysteresis under cyclic loading, critical for seismic and vibration applications [7]. Kong et al. [10] demonstrated that higher annealing temperatures

reduce residual stresses and improve superelastic recovery, while pre-deformation promotes favorable martensitic variant reorientation. Ternary NiTi-based alloys extend transformation temperature ranges and improve functional stability. Bigelow et al. [11] studied Ni_{50.5}Ti_{27.2}Hf_{22.3}, demonstrating high transformation temperatures and stable superelastic behavior for high-temperature actuators. Santosh et al. [12] showed that Si addition promotes grain refinement and reduces impurity inclusions, while Liu et al. [13] found that Cu substitution alters transformation sequences and improves strain-sensing capabilities.

2.2.2 Cu-Based Systems:

Cu-based alloys provide cost-effective alternatives to NiTi. Ito et al. [14] investigated Mn-rich Cu-Mn-Al alloys, revealing robust martensitic transformations but lower ductility than NiTi. Fakhraei et al. [15] demonstrated that higher Al content improves thermal stability but reduces ductility in Cu-Al-Fe alloys. Saud et al. [16] showed that Ta additions enhance damping behavior and shape memory response by stabilizing martensitic variants. While these alloys exhibit lower recoverable strain and functional fatigue resistance compared to NiTi, their low cost and ease of processing make them attractive for large-scale applications where cost efficiency outweighs absolute performance.

2.2.3 Fe-Based, High-Entropy, and Magnetic Systems:

Fe-based SMAs offer a compelling balance of cost, strength, and environmental durability for structural applications [17], [4]. High-entropy alloys (HEAs) present tunable transformation characteristics, though functional fatigue and processing scalability remain challenges [18]. Magnetic SMAs like Ni-Mn-Ga enable rapid actuation but face brittleness and narrow transformation range limitations [19].

2.2.4 Applications and Engineering Implementation:

Biomedical devices represent the earliest and most successful SMA applications, with NiTi alloys dominating due to their biocompatibility, superelasticity, and corrosion resistance. Stents and orthodontic wires exploit NiTi's large recoverable strains and near-constant recovery forces, improving patient comfort and reducing clinical interventions [2]. In civil and structural engineering, SMAs provide seismic resilience through cable-restrained bearing systems and reinforced concrete shear walls that demonstrate superior re-centering and energy dissipation capabilities [3], [4]. Embedded SMA fibers in concrete composites improve crack closure, stiffness retention, and damping performance, enabling self-healing and prestressing applications [20]. Aerospace and automotive sectors increasingly integrate SMAs as compact, high-force actuators and morphing elements. High-temperature NiTiHf alloys enable reliable actuation in demanding environments such as turbine components [11]. Consumer and assistive technologies leverage SMAs in tactile displays for visually impaired users and precision micro-actuators [21], [22]. Integration into polymer composites enhances structural damping, impact resistance, and energy absorption through reversible stress recovery, opening pathways for advanced damping systems and adaptive structural components [9].

2.3 Fundamental Properties of Shape Memory Alloys:

2.3.1 Transformation Temperatures:

The functionality of SMAs is governed by transformation temperatures, which define the start and finish of martensitic (Ms, Mf) and austenitic (As, Af) transformations. These temperatures vary with composition, processing, and heat treatment. For example, NiTi-based alloys display transformation ranges from sub-zero to above 100°C, with additions such as Hf raising transformation temperatures significantly [11], while Si additions refine microstructure without drastically shifting transformation points [12]. In Cu-based systems, Al and Mn content strongly influence stability and transformation ranges [15], [14]. Control over transformation temperatures allows designers to match SMA activation to environmental and operational demands.

2.3.2 Shape Memory Recovery:

Shape memory recovery describes the ability of SMAs to return to their original form upon heating. Recovery depends on transformation completeness, training, and cycling history. Liu et al. [13] demonstrated enhanced strain-sensing properties in NiTiCu systems due to stable recovery behavior. Gopalakrishnan et al. [9] reported that embedding SMAs in composites improves recovery stress, enabling self-healing and prestressing applications. In high-temperature systems such as NiTiHf, recovery is sustained over elevated cycles [11], confirming the compositional influence on recovery stability.

2.3.3 Mechanical Properties:

SMA exhibit unique mechanical properties, including recoverable strains of up to 8–10%, superelastic hysteresis, and high damping capacity. Biffi et al. [22] investigated NiTi micro-elements, showing their capability to generate large recoverable deformations suitable for actuation. In civil engineering, SMA fibers enhance stiffness retention and mechanical toughness of composites [20]. Cu-based alloys typically show lower ductility and recoverable strain compared to NiTi but are more cost-effective [14].

2.3.4 Strain Rate Effects:

SMA response is sensitive to strain rate due to thermomechanical coupling. Qian et al. [7] demonstrated that higher strain rates increase transformation stresses and hysteresis loop areas in NiTi wires. Roh [23] confirmed that thermo-mechanical models must incorporate strain-rate effects to capture pseudoelastic behavior accurately. These findings are essential for dynamic applications such as seismic dampers, where strain rates vary rapidly.

2.3.5 Fatigue and Cycling Performance:

Fatigue and cycling stability are critical for long-term use of SMAs. Simoes et al. [24] showed that fatigue crack growth in NiTi is influenced by stress amplitude, environmental effects, and microstructural defects. Mehrpouya et al. [8] emphasized that additive manufacturing strategies can tune microstructures to improve functional fatigue in architected SMA lattices. Kong et al. [10] demonstrated that pre-deformation and annealing improve superelastic cycling by stabilizing martensitic variants. Understanding cycling behavior is vital for ensuring SMA reliability in biomedical implants, actuators, and structural systems.

III. METHODOLOGY

3.1 Literature Search and Selection Strategy:

A systematic literature search was conducted to identify relevant studies on shape memory alloys published primarily between 2000 and 2025. The search strategy employed multiple electronic databases including Web of Science, Scopus, IEEE Xplore, and Google Scholar. Search terms included combinations of "shape memory alloy," "superelasticity," "martensitic transformation," "NiTi," "Nitinol," "Cu-based SMA," "Fe-based SMA," and "high-entropy alloys" using Boolean operators (AND, OR).

Inclusion Criteria:

- Peer-reviewed journal articles and conference proceedings
- Studies reporting experimental data on SMA properties and performance
- Articles focusing on metallic shape memory alloys
- Publications in English language
- Studies with clear methodology and quantifiable results

Exclusion Criteria:

- Review articles without original experimental data (except seminal review papers)
- Studies focusing solely on theoretical modeling without experimental validation
- Conference abstracts without full papers
- Studies on polymeric SMAs (outside scope of this review)
- Publications with insufficient technical detail for analysis

3.2 Data Extraction and Categorization:

From each selected study, the following information was systematically extracted and documented:

Technical Parameters:

- Alloy composition and processing conditions
- Transformation temperatures (M_s , M_f , A_s , A_f)

- Shape memory recovery percentages and strain levels
- Mechanical properties (strength, ductility, cycling performance)
- Processing methods and heat treatments

Performance Metrics:

- Functional properties (recovery strain, transformation stress)
- Durability characteristics (fatigue life, cycling stability)
- Environmental resistance (corrosion, temperature stability)
- Manufacturing feasibility and processing challenges

Application Context:

- Primary application domains (biomedical, aerospace, civil engineering)
- Commercial deployment status
- Cost considerations and economic factors
- Technology readiness level indicators

3.3 Alloy System Classification:

Studies were systematically categorized into distinct alloy families based on primary alloying elements:

- NiTi-based systems: Binary NiTi, NiTi-Hf, NiTi-Si, NiTi-Cu variants
- Cu-based systems: Cu-Al-Fe, Cu-Al-Ni, Cu-Mn-Al compositions with various additions (Ta, etc.)
- Fe-based systems: Fe-Mn-Si-Cr-Ni alloys designed for structural applications
- High-entropy alloys: Multi-component systems (CrMnFeCoNi variants)
- Magnetic SMAs: Ni-Mn-Ga and related magnetically actuated systems

This classification enabled systematic comparison while recognizing the fundamental differences between alloy families.

3.4 Qualitative Comparative Analysis Framework:**3.4.1 Multi-Dimensional Assessment Approach:**

A comprehensive comparative analysis was conducted across seven key dimensions:

- 1) Thermal Characteristics: Transformation temperature ranges and thermal stability
- 2) Functional Performance: Shape memory effect, recovery strain, and cycling behavior
- 3) Mechanical Properties: Strength, ductility, and processability
- 4) Economic Factors: Raw material costs, processing complexity, and commercial availability
- 5) Application Domains: Current market deployment and suitability for different sectors
- 6) Manufacturing Readiness: Fabrication methods and processing maturity
- 7) Research Status: Technology readiness level and future development potential

3.4.2 Performance Rating System:

A standardized rating scale was developed to enable consistent evaluation across different alloy systems:

- Excellent (9-10): Superior performance with established commercial success
- Very Good (7-8): High performance with demonstrated applications
- Good (5-6): Adequate performance with limited commercial use

- Moderate (3-4): Below-average performance, research/prototype stage
- Poor (1-2): Inadequate performance, fundamental research only
- Unknown: Insufficient data available for assessment

3.4.3 Comparative Methodology:

For each dimension, alloy systems were evaluated using:

- Literature-based evidence: Performance data and characteristics reported in selected studies
- Quantitative benchmarks: Specific numerical criteria (e.g., >8% recovery strain for "excellent")
- Application context: Commercial deployment and market penetration indicators
- Technology maturity: Research volume, development stage, and industrial readiness

3.5 Data Analysis and Synthesis:

Results were organized into structured comparison tables for each evaluation dimension. This approach facilitated:

- Direct system-to-system comparisons
- Identification of performance trade-offs
- Recognition of application-specific advantages
- Assessment of research gaps and opportunities

3.5.1 Pattern Recognition:

Cross-dimensional analysis was conducted to identify:

- Performance hierarchies: Overall ranking of systems across multiple criteria
- Trade-off relationships: Inverse correlations between different properties (e.g., cost vs. performance)
- Application matching: Alignment between system capabilities and market requirements
- Development trends: Evolution of different technologies over time

3.6 Quality Assessment and Validation:

3.6.1 Literature Quality Evaluation:

Selected studies were assessed for:

- Experimental rigor and methodology clarity
- Sample sizes and statistical treatment
- Reproducibility of results
- Peer review quality and journal impact

3.6.2 Classification Validation:

The alloy system categorization was validated through:

- Consistency with established metallurgical classifications
- Cross-referencing with multiple literature sources
- Expert knowledge from foundational SMA textbooks and reviews
- Verification of compositional ranges and processing methods

3.6.3 Rating System Assumptions:

The comparative rating system assumes:

- Linear relationship between numerical scores and qualitative categories
- Equal weighting of different performance criteria
- Comparability across different experimental conditions
- Relevance of current performance indicators to future applications

3.6.4 Analytical Framework Justification:

The qualitative comparative analysis approach was selected over quantitative meta-analysis for several reasons:

- 1) Data heterogeneity: Extreme variability in experimental conditions, sample preparations, and measurement protocols across studies
- 2) System diversity: Fundamental differences between alloy families make statistical pooling inappropriate
- 3) Scope appropriateness: Systematic comparison better suited for undergraduate-level research scope
- 4) Practical utility: Comparative framework provides actionable insights for material selection and research prioritization

IV. RESULTS

TABLE 1
TRANSFORMATION TEMPERATURE RANGES AND THERMAL CHARACTERISTIC

Alloy System	Transformation Temperature Range	Thermal Stability	Key Studies	Notes
Binary NiTi	Room temperature to ~100°C	Good	Qian et al. (2013), Kong et al. (2024)	Most studied system; highly tunable through composition
NiTi-Hf	126°C to >200°C	Excellent	Bigelow et al. (2022)	High-temperature applications; stable at elevated temperatures
NiTi-Si	342-380K (69-107°C)	Good	Santosh et al. (2024)	Cost-effective alternative to Hf additions
Cu-Al-Fe	455-617K (182-344°C)	Good	Fakhraei et al. (2020)	Highest temperature capability among systems studied
Cu-Al-Ni-Ta	Not specified	Enhanced	Saud et al. (2017)	Improved thermal stability through Ta additions
Cu-Mn-Al	125-316K (-148-43°C)	Moderate	Ito et al. (2025)	Low-temperature applications; novel system
Fe-based	Variable	Good in corrosive environments	Kulkarni et al. (2025)	Designed for structural applications
High-Entropy Alloys	210-350K (-63-77°C)	Under investigation	Lim et al. (2025)	Experimental stage; tunable through composition

As seen in Table 1, the transformation temperature characteristics reveal distinct patterns across different alloy families. NiTi-based systems dominate the moderate to high-temperature range, with Hf additions enabling the highest operating temperatures among all systems studied. Cu-based systems demonstrate the broadest temperature range capability, spanning from very low temperatures in Cu-Mn-Al compositions to very high temperatures in Cu-Al-Fe variants. Fe-based systems are designed primarily for structural durability rather than optimized for specific temperature ranges, reflecting their intended application in civil engineering contexts. High-entropy alloys represent an emerging field with potentially tunable properties, though their transformation characteristics remain under investigation.

TABLE 2
SHAPE MEMORY EFFECT AND RECOVERY PERFORMANCE

Alloy System	Recovery Strain (%)	Recovery Completeness	Cycling Stability	Key Studies	Performance Level
Binary NiTi	8-10%	Excellent (>95%)	Very Good	Multiple studies	Excellent
NiTi-Hf	Comparable to binary	Very Good (~90-95%)	Excellent	Bigelow et al. (2022)	Very Good
NiTi-Si	Not reported	Not specified	Under investigation	Santosh et al. (2024)	Unknown
Cu-Al-Fe	Variable (26-84%)	Moderate	Fair	Fakhraei et al. (2020)	Moderate
Cu-Al-Ni-Ta	Up to 100% (1st cycle)	Excellent	Good with training	Saud et al. (2017)	Good
Cu-Mn-Al	1.3% (single crystal)	Limited	Poor	Ito et al. (2025)	Poor
Fe-based	Not specified	Good	Good	Nasiri & Ghassemieh (2025)	Good
High-Entropy Alloys	1.2% maximum	Limited	Under study	Lim et al. (2025)	Poor

The shape memory recovery performance data in Table 2 reveals significant disparities among different alloy systems. Binary NiTi clearly outperforms all other systems in terms of both recovery strain magnitude and completeness, maintaining its position as the benchmark material. Cu-based systems exhibit high variability in performance, though optimized compositions such as Cu-Al-Ni-Ta are approaching NiTi performance levels under specific conditions. Novel systems including Cu-Mn-Al and high-entropy alloys currently demonstrate limited recovery capabilities, with maximum strains below 1.5% reported in the literature. Fe-based systems prioritize structural properties over maximum recovery performance, reflecting their design philosophy for civil engineering applications where mechanical strength and durability take precedence over shape memory functionality.

TABLE 3
MECHANICAL PROPERTIES AND PROCESSABILITY

Alloy System	Strength Level	Ductility	Machinability	Processing Challenges	Key Studies
Binary NiTi	High	Good	Poor (strain hardening)	Surface oxidation, Ni evaporation	Immanuel et al. (2022)
NiTi-Hf	Very High	Good	Poor	High-temperature processing	Bigelow et al. (2022)
NiTi-Si	Good	Good	Moderate	Impurity control	Santosh et al. (2024)
Cu-Al-Fe	High (>800 MPa)	Poor to Moderate	Moderate	Brittleness issues	Fakhraei et al. (2020)
Cu-Al-Ni-Ta	Good	Improved	Good	Porosity control	Saud et al. (2017)
Cu-Mn-Al	Moderate	Good (cold workable)	Good	Limited transformation strain	Ito et al. (2025)
Fe-based	High	Good	Good	Corrosion in chlorides	Kulkarni et al. (2025)
High-Entropy Alloys	Variable	Good	Under study	Complex processing	Lim et al. (2025)

As Table 3 shows, the mechanical properties and processability characteristics demonstrate significant variation across alloy families. NiTi systems generally offer the best combination of strength and functional properties but are difficult to machine, presenting manufacturing challenges that affect production costs and design flexibility. Cu-based systems are more processable and easier to work with using conventional manufacturing methods, but often suffer from brittleness that limits their reliability in demanding structural applications. Fe-based systems offer good structural properties and processability, benefiting from decades of established steel processing knowledge and infrastructure, which facilitates their adoption in large-scale civil engineering applications. Novel systems such as high-entropy alloys require further development for practical processing, as their complex compositions and limited understanding of processing-property relationships present significant barriers to manufacturing scalability and commercial implementation.

TABLE 4
COST AND ECONOMIC CONSIDERATIONS

Alloy System	Raw Material Cost	Processing Cost	Commercial Availability	Cost-Effectiveness Rating
Binary NiTi	High (Ni content)	High	Excellent	Moderate
NiTi-Hf	Very High (Hf addition)	Very High	Limited	Low
NiTi-Si	Moderate	Moderate	Limited	Good
Cu-Al-Fe	Low	Low to Moderate	Good	Excellent
Cu-Al-Ni-Ta	Low to Moderate	Moderate	Limited	Good
Cu-Mn-Al	Very Low	Low	Research stage	Excellent
Fe-based	Low	Low	Growing	Excellent
High-Entropy Alloys	Variable	High	Research stage	Poor

The economic considerations in Table 4 reveal stark disparities in cost-effectiveness across different alloy systems. Cu-based and Fe-based systems offer significant cost advantages over NiTi, with raw material costs often an order of magnitude lower, making them attractive for large-scale applications where budget constraints are critical. Hf additions make NiTi-Hf systems very expensive, with hafnium costs exceeding \$200/kg compared to less than \$10/kg for copper-based materials, significantly limiting their commercial applications to specialized high-value aerospace and defense sectors where performance justifies the premium pricing. Novel systems including Cu-Mn-Al and high-entropy alloys show promise for cost reduction due to their use of abundant and inexpensive constituent elements, but these materials need further development before they can achieve commercial viability and reliable performance. Commercial availability strongly influences practical cost-effectiveness, as established supply chains, processing infrastructure, and technical expertise for mature systems like binary NiTi provide economic advantages that extend beyond raw material costs alone, affecting the total cost of ownership for SMA-based solutions.

TABLE 5
PRIMARY APPLICATIONS AND MARKET SEGMENTS

Alloy System	Biomedical	Aerospace/ Automotive	Civil Engineering	Consumer/Assistive	Research Priority
Binary NiTi	Dominant (stents, orthodontics)	Moderate (actuators)	Growing (dampers)	Good (tactile displays)	Optimization
NiTi-Hf	Limited	Strong (high-temp actuators)	Limited	None	Specialization
NiTi-Si	Potential	Potential	Limited	Limited	Development
Cu-Al-Fe	None (not biocompatible)	Limited	Good (high-temp)	Limited	Optimization
Cu-Al-Ni-Ta	Limited	Potential	Moderate	Limited	Development
Cu-Mn-Al	None	None	None	None	Fundamental research
Fe-based	None	Limited	Dominant (structures)	None	Implementation
High-Entropy Alloys	None	None	None	None	Fundamental research

The application domains and market penetration patterns in Table 5 reflect distinct specialization among different alloy systems. Binary NiTi dominates biomedical applications due to its superior biocompatibility and reliability, with well-established use in stents, orthodontic devices, and surgical instruments that have demonstrated long-term clinical success and regulatory approval. NiTi-Hf serves specialized high-temperature aerospace applications where extreme operating conditions and stringent performance requirements justify the material's premium cost, particularly in actuators and morphing structures subjected to temperatures exceeding 200°C. Fe-based systems are becoming preferred for civil engineering applications due to their favorable combination of cost-effectiveness and corrosion resistance, enabling large-scale deployment in seismic retrofitting, bridge bearings, and reinforced concrete systems where economic constraints would prohibit NiTi use. Cu-based systems fill mid-range industrial applications where biocompatibility is not required, offering a compromise between the high performance of NiTi and the low cost of Fe-based alternatives for actuators, dampers, and mechanical components in non-medical sectors. Novel systems including Cu-Mn-Al alloys and high-entropy alloys remain primarily in research phases, with limited commercial deployment as they require fundamental property optimization and processing development before transitioning from laboratory demonstrations to practical engineering applications.

TABLE 6
MANUFACTURING AND FABRICATION METHODS

Alloy System	Conventional Melting	Powder Metallurgy	Additive Manufacturing	Special Processing	Key Studies
Binary NiTi	Standard	Good	Excellent	Extensive heat treatment	Mehrpouya et al. (2024)
NiTi-Hf	Vacuum required	Limited	Developing	Complex thermal processing	Bigelow et al. (2022)
NiTi-Si	Modified VIM	Good	Potential	Argon backfilling	Santosh et al. (2024)
Cu-Al-Fe	Standard	Good	Limited	Homogenization critical	Fakhraei et al. (2020)
Cu-Al-Ni-Ta	Standard	Excellent	Limited	Microwave sintering	Saud et al. (2017)
Cu-Mn-Al	Standard	Good	Unknown	Hot rolling required	Ito et al. (2025)
Fe-based	Standard	Good	Potential	Heat treatment optimization	Kulkarni et al. (2025)
High-Entropy Alloys	Induction melting	Limited	Unknown	Complex composition control	Lim et al. (2025)

As seen in Table 6, the manufacturing and fabrication capabilities vary considerably across different alloy systems, reflecting their relative technological maturity and processing complexity. NiTi systems have the most developed manufacturing processes, especially for additive manufacturing techniques such as selective laser melting and electron beam melting, which enable complex geometries, lattice structures, and functionally graded designs that enhance performance beyond what conventional processing can achieve. Cu-based systems generally use conventional processing methods including casting, powder metallurgy, and thermomechanical treatment, with good powder metallurgy potential that enables near-net-shape manufacturing and reduced material waste, though homogenization treatments remain critical for achieving consistent properties. Fe-based systems leverage existing steel processing knowledge and infrastructure, allowing for cost-effective manufacturing using established melting, forging, and heat treatment procedures that require minimal specialized equipment or expertise, facilitating their adoption in large-scale structural applications. Novel systems including high-entropy alloys require specialized processing development due to their complex multi-component compositions, with challenges in achieving compositional uniformity, controlling phase formation, and establishing reproducible processing-property relationships that must be resolved before these materials can transition from laboratory-scale production to industrial manufacturing.

TABLE 7
RESEARCH MATURITY AND FUTURE POTENTIAL

Alloy System	Technology Readiness Level	Research Volume	Commercial Maturity	Future Growth Potential	Key Challenges
Binary NiTi	9 (Deployed)	Extensive	Mature	Moderate (optimization)	Cost reduction, processing
NiTi-Hf	7-8 (Demonstrated)	Moderate	Niche market	Good (aerospace growth)	Cost, processing complexity
NiTi-Si	4-5 (Development)	Limited	Emerging	Good (cost-effective alternative)	Property optimization
Cu-Al-Fe	6-7 (Prototype)	Moderate	Limited commercial	Moderate	Brittleness, reliability
Cu-Al-Ni-Ta	5-6 (Development)	Limited	Research/pilot	Good (improved Cu-based)	Scale-up, optimization
Cu-Mn-Al	3-4 (Research)	Very Limited	None	Uncertain	Fundamental properties
Fe-based	6-7 (Prototype)	Growing	Emerging	Excellent (infrastructure)	Corrosion, recovery strain
High-Entropy Alloys	2-3 (Research)	Limited	None	High (long-term)	Fundamental understanding

The research maturity and technological readiness levels reveal significant disparities in commercial development across alloy systems. Binary NiTi is the only fully mature commercial technology, having achieved widespread market deployment with established supply chains, standardized processing protocols, and regulatory approvals across multiple application sectors, particularly in the biomedical device industry. Fe-based systems show the highest growth potential due to infrastructure applications, as increasing emphasis on seismic resilience and sustainable construction drives demand for cost-effective shape memory solutions in civil engineering, where the large-scale material requirements favor economically viable alternatives to NiTi. Novel systems including high-entropy alloys and Cu-Mn-Al compositions require significant fundamental research before practical implementation becomes feasible, as these materials remain in early-stage laboratory investigation with limited understanding of their transformation mechanisms, long-term stability, and processing-property relationships. NiTi variants such as NiTi-Hf and NiTi-Si serve specialized niches where their unique capabilities justify development efforts, but face cost and processing barriers that limit their market expansion beyond high-value applications in aerospace and defense sectors, restricting their adoption despite demonstrated technical advantages in specific operating environments.

This comparative analysis reveals several important patterns:

1. Performance Hierarchy: Binary NiTi remains the gold standard for functional properties, followed by NiTi variants, then optimized Cu-based systems, with novel systems trailing significantly.
2. Application-Specific Optimization: Different systems excel in different domains - NiTi for biomedical, NiTi-Hf for aerospace, Fe-based for civil engineering, and Cu-based for cost-sensitive applications.
3. Trade-offs: There are clear trade-offs between performance, cost, and processability. No single system excels in all areas.
4. Research Gaps: Novel systems (HEAs, Cu-Mn-Al) show promise but require substantial fundamental research before practical implementation.
5. Manufacturing Maturity: Processing and manufacturing capabilities strongly influence commercial viability, with NiTi having the most developed infrastructure.

Rating Scale and Classification Criteria

TABLE 8
COMPREHENSIVE RATING SCALE AND CLASSIFICATION CRITERIA FOR SHAPE MEMORY ALLOYS

Rating Category	Scale	Performance Criteria	Cost-Effectiveness Criteria	TRL Mapping	Application Suitability
Excellent	09-Oct	<ul style="list-style-type: none"> • Recovery strain >8% • >95% shape recovery • Stable over >1000 cycles • Commercial deployment successful 	Raw materials <\$5/kg, simple processing, high availability	TRL 9 (Deployed): Commercial products in widespread use	Dominant: >60% market share in application area
Very Good	07-Aug	<ul style="list-style-type: none"> • Recovery strain 5-8% • 85-95% shape recovery • Stable over 500+ cycles • Proven in specialized applications 	Moderate cost materials, standard processing, good availability	TRL 7-8 (Demonstrated): System prototypes demonstrated in operational environment	Strong: 20-60% market share or proven performance advantage
Good	05-Jun	<ul style="list-style-type: none"> • Recovery strain 2-5% • 70-85% shape recovery • Moderate cycling stability • Limited commercial use 	Moderate cost materials, standard processing, good availability	TRL 5-6 (Development): Technology validated in relevant environment	Good: 5-20% market share or demonstrated capability
Moderate	03-Apr	<ul style="list-style-type: none"> • Recovery strain 1-2% • 50-70% shape recovery • Limited cycling data • Research/prototype stage 	Higher cost materials or processing, limited availability	TRL 3-4 (Research): Analytical and experimental proof of concept	Moderate: <5% market share or limited demonstrations
Poor	01-Feb	<ul style="list-style-type: none"> • Recovery strain <1% • <50% shape recovery • Poor cycling stability • Fundamental research only 	Expensive materials (>\$50/kg), complex processing, very limited availability	TRL 1-2 (Basic Research): Basic principles observed and reported	Limited/None: No commercial presence or unsuitable properties
Unknown	-	<ul style="list-style-type: none"> • Insufficient data available • Properties not reported • Early research stage 	Insufficient data	Insufficient data	Insufficient data

V. DISCUSSION

5.1 Performance hierarchy and material selection:

The comparative analysis reveals a clear performance hierarchy among SMA systems, with binary NiTi maintaining its position as the benchmark for functional properties. This dominance stems from the unique combination of large recoverable strains (8-10%), excellent shape recovery (>95%), and robust cycling stability demonstrated across multiple studies [7], [10], [22].

The crystallographic compatibility between B2 austenite and B19' martensite phases in NiTi enables the reversible transformation strains that underpin its superior performance.

However, the analysis also demonstrates that no single alloy system excels across all evaluation criteria, necessitating application-specific material selection. While NiTi variants like NiTi-Hf achieve transformation temperatures exceeding 200°C suitable for aerospace applications [11], they come at significant cost penalties that limit widespread adoption. Conversely, Cu-based systems, despite lower absolute performance metrics, offer compelling alternatives where cost-effectiveness outweighs maximum functionality.

The emergence of optimized Cu-based compositions, particularly Cu-Al-Ni-Ta systems showing up to 100% first-cycle recovery [16], indicates that performance gaps between alloy families may be narrowing through compositional engineering and processing optimization. This trend suggests that future developments may challenge the traditional NiTi dominance in specific application niches.

5.2 Application-driven technology development:

The analysis reveals distinct application domains driving different aspects of SMA technology development. Biomedical applications continue to leverage NiTi's unique combination of biocompatibility, superelasticity, and corrosion resistance. The success of NiTi stents and orthodontic devices [2] has established both the commercial viability and technical requirements for biomedical SMAs. The consistent stress recovery over extended strain ranges addresses critical clinical needs for patient comfort and reduced intervention frequency.

Civil engineering applications present different requirements, emphasizing cost-effectiveness, structural integrity, and environmental durability over maximum functional performance. The growing adoption of Fe-based SMAs in seismic applications [4], [3] demonstrates how application-specific optimization can overcome traditional performance limitations. The self-centering capabilities and energy dissipation characteristics of Fe-based systems align well with earthquake resilience requirements, even though their transformation strains are lower than NiTi systems.

Aerospace applications drive high-temperature SMA development, with NiTi-Hf systems achieving stable operation above 200°C [11]. The demanding environmental conditions and stringent reliability requirements justify the higher costs associated with specialized compositions. The morphing structures and adaptive vibration control systems [26] represent applications where SMA functionality enables entirely new engineering solutions rather than simply replacing conventional materials.

5.3 Manufacturing and processing implications:

The comparative analysis highlights significant disparities in manufacturing readiness across alloy systems. NiTi's extensive processing infrastructure, particularly in additive manufacturing [8], provides significant competitive advantages through design flexibility and customization capabilities. The development of complex lattice structures and graded porosity designs demonstrates how advanced manufacturing can enhance fundamental material properties.

However, processing challenges remain significant across all systems. The poor machinability of NiTi due to strain hardening effects [25] continues to limit cost-effective production for many applications. The requirement for specialized cooling and lubrication techniques adds complexity and cost to manufacturing processes. These challenges may create opportunities for alternative systems with better processability, even if their functional properties are somewhat lower.

The modified processing approaches for newer systems, such as the argon backfilling technique for NiTi-Si alloys [12] and microwave sintering for Cu-Al-Ni-Ta systems [16], indicate ongoing innovation in manufacturing methods. These developments may eventually impact the relative competitiveness of different alloy families by addressing cost and scalability limitations.

5.4 Economic and sustainability considerations:

The stark cost differences between alloy systems significantly influence commercial adoption patterns. Raw material costs ranging from <\$5/kg for Cu-based systems to >\$200/kg for NiTi-Hf systems (as evidenced by hafnium pricing) create distinct market segments with different cost sensitivity. The analysis suggests that applications requiring the highest performance justify premium pricing, while cost-sensitive applications drive development of alternative systems.

Fe-based systems present particularly interesting sustainability implications due to their recyclability and abundance of constituent elements. The improved corrosion resistance demonstrated in heat-treated Fe-SMAs [17] addresses one of the

traditional limitations of iron-based systems. As infrastructure applications emphasize lifecycle considerations and environmental impact, the sustainability advantages of Fe-based systems may become increasingly important.

The energy consumption associated with different processing routes also varies significantly. Conventional melting and thermomechanical processing require substantial energy inputs, particularly for high-temperature processing of NiTi-Hf systems. Powder metallurgy routes, particularly successful for Cu-Al-Ni-Ta systems, may offer energy advantages while enabling net-shape processing that reduces material waste.

5.5 Technological integration and system-level considerations:

The integration of SMAs into composite systems represents a significant opportunity for expanding application domains. The enhancement of damping capacity, crack closure, and impact resistance in SMA-reinforced composites [9], [20] demonstrates how SMA functionality can be leveraged at the system level rather than relying solely on monolithic components.

However, the analysis reveals that successful integration requires careful consideration of activation mechanisms, thermal management, and mechanical compatibility. The strain-rate sensitivity of SMA behavior [7], [23] indicates that dynamic applications require sophisticated control systems to achieve consistent performance. The development of predictive models that account for thermomechanical coupling becomes critical for reliable system design.

The fatigue and fracture behavior of SMAs [24], [27] remains a limiting factor for many applications. The complex interaction between transformation-induced strains, stress concentrators, and environmental effects requires continued research attention. The phase-field modeling approaches for fatigue crack growth represent promising tools for predictive design, but validation across different alloy systems and loading conditions remains incomplete.

VI. CONCLUSION

This comprehensive comparative analysis of shape memory alloy systems reveals several critical insights for material selection and application development. The performance hierarchy clearly establishes binary NiTi as the benchmark for functional properties, achieving 8-10% recoverable strain with >95% shape recovery and excellent cycling stability. However, the analysis demonstrates that optimal material selection depends on application-specific requirements rather than absolute performance metrics.

The systematic evaluation across seven dimensions reveals distinct competitive advantages for different alloy families. NiTi-Hf systems enable high-temperature applications above 200°C for aerospace actuators, justifying their premium costs through unique capabilities. Cu-based systems, particularly optimized Cu-Al-Ni-Ta compositions, offer cost-effective alternatives with recovery performance approaching NiTi levels in specific applications. Fe-based systems provide structural integration opportunities for civil engineering applications where cost, corrosion resistance, and compatibility with existing materials outweigh maximum recovery performance.

The analysis also identifies clear trade-off relationships that guide material selection. High-performance systems invariably involve higher costs and processing complexity, while cost-effective alternatives require compromises in functional properties. Manufacturing readiness varies significantly across systems, with NiTi benefiting from extensive processing infrastructure while emerging systems require specialized development.

6.1 Implications for Application and Testing

The findings have several important implications for SMA application and characterization. First, standardized testing protocols are needed to enable reliable comparisons across different alloy systems. The current heterogeneity in experimental conditions, measurement protocols, and reporting standards limits the ability to make quantitative performance comparisons.

Second, application-specific performance criteria should guide material selection rather than generic property optimization. Biomedical applications require biocompatibility and reliability over maximum transformation strain, while civil engineering applications prioritize cost-effectiveness and environmental durability. Aerospace applications justify premium materials for specialized high-temperature performance.

Third, system-level integration considerations often prove more critical than monolithic material properties. The successful implementation of SMA-reinforced composites and hybrid systems demonstrates that functional benefits can be achieved through strategic integration rather than relying solely on maximum individual component performance.

The analysis also highlights the importance of considering the entire material lifecycle, including processing requirements, manufacturing scalability, and end-of-life considerations. Sustainability factors, particularly relevant for Fe-based systems, may become increasingly important as environmental considerations influence material selection decisions.

6.2 Practical Implications:

For researchers and engineers working with SMAs, this analysis provides several practical guidelines. Material selection should begin with clearly defined application requirements and constraints rather than pursuing maximum theoretical performance. The rating framework developed in this study offers objective criteria for comparing different systems across multiple performance dimensions.

For industrial applications, the analysis suggests that binary NiTi remains the preferred choice for demanding functional applications where cost is secondary to performance. However, optimized alternative systems may provide viable solutions for cost-sensitive applications or where specific environmental or processing requirements favor non-NiTi options.

The identification of research maturity levels across different systems also guides research investment priorities. While binary NiTi focuses on optimization and cost reduction, emerging systems like high-entropy alloys require fundamental property development before practical implementation becomes viable.

6.3 Technological Development Pathways:

The analysis reveals several promising directions for SMA technology advancement. Additive manufacturing capabilities, particularly well-developed for NiTi systems, enable complex geometries and functional gradients that enhance overall system performance beyond what is achievable with conventional processing.

Compositional optimization within established alloy families shows significant potential, as demonstrated by the improved performance of Cu-Al-Ni-Ta systems compared to baseline Cu-based alloys. This suggests that systematic alloying approaches may narrow performance gaps between different system families.

Integration with smart systems and control technologies offers opportunities to compensate for material limitations through system-level optimization. Predictive control systems that account for strain-rate sensitivity and thermal management can enhance reliability and performance consistency across different operating conditions.

6.4 Limitations:

Several limitations must be acknowledged in this comparative analysis. The heterogeneity of experimental conditions and measurement protocols across the reviewed literature limits the precision of quantitative comparisons. Different testing standards, sample preparation methods, and environmental conditions contribute to variability that cannot be completely eliminated through systematic analysis.

The rating system developed for this study, while providing objective criteria, necessarily involves subjective judgments about the relative importance of different performance criteria. The equal weighting of different evaluation dimensions may not reflect the actual importance of these factors for specific applications.

The scope of this review, while comprehensive across major alloy families, excludes some specialized systems and emerging compositions that may prove significant in future developments. The focus on metallic systems excludes polymeric and ceramic shape memory materials that serve related application needs.

Temporal bias may also influence the analysis, as newer systems appear less developed due to limited research history rather than fundamental limitations. The rapid pace of development in some areas means that current assessments may quickly become outdated.

The analysis relies primarily on literature reports rather than direct experimental comparison under standardized conditions. This introduces potential inconsistencies due to different measurement protocols, sample qualities, and testing environments across different research groups.

6.5 Future Research Directions:

Several critical research needs emerge from this analysis. Standardization of testing protocols and performance metrics would greatly improve the reliability of comparative assessments and enable more informed material selection decisions.

Development of predictive models that link processing conditions to functional properties across different alloy systems would accelerate optimization efforts.

Investigation of hybrid and composite systems represents a particularly promising area, as demonstrated by the success of SMA-reinforced concrete and polymer composites. Understanding the interaction between SMA components and matrix materials could enable new applications that leverage system-level properties rather than individual material capabilities.

Environmental degradation mechanisms require more systematic investigation across all alloy systems. Understanding how different systems respond to thermal cycling, corrosive environments, and mechanical fatigue under real-world conditions is essential for reliable engineering applications.

The integration of machine learning and high-throughput experimental approaches offers opportunities for accelerated alloy development and property optimization. The complex relationships between composition, processing, and properties in SMAs make them suitable candidates for data-driven materials discovery approaches.

Finally, lifecycle assessment and sustainability considerations should be integrated into comparative evaluations as environmental concerns increasingly influence material selection decisions. Understanding the full environmental impact of different SMA systems, from raw material extraction through end-of-life disposal, will become increasingly important for responsible engineering practice.

This comparative analysis provides a foundation for informed material selection and identifies key areas for future research that can advance the practical application of shape memory alloys across their diverse application domains.

REFERENCES

- [1] Grand View Research, "Smart materials market size, share & trends analysis report," 2024.
- [2] L. Petrini and F. Migliavacca, "Biomedical applications of shape memory alloys," *J. Metall.*, vol. 2011, pp. 1-15, 2011.
- [3] Y. Liu, H. Yang, Z. Wang, and S. Li, "Seismic performance of SMA cable-restrained bearing systems," *Eng. Struct.*, vol. 298, 2024.
- [4] M. R. Nasiri and M. Ghassemieh, "Seismic performance of Fe-SMA reinforced concrete shear walls," *J. Build. Eng.*, vol. 82, 2025.
- [5] K. Otsuka and C. M. Wayman, *Shape Memory Materials*. Cambridge, UK: Cambridge University Press, 1998.
- [6] X. Wang, B. Xu, and Z. Yue, "Temperature memory effect in NiTi shape memory alloy," *Acta Mater.*, vol. 59, pp. 1037-1045, 2011.
- [7] L. Qian, Q. Sun, and X. Xiao, "Role of phase transition in the unusual microwear behavior of superelastic NiTi shape memory alloy," *Wear*, vol. 301, pp. 309-317, 2013.
- [8] M. Mehrpouya, A. Gisario, and M. Elahinia, "Laser powder bed fusion of NiTi shape memory alloy lattice structures," *J. Manuf. Process.*, vol. 92, pp. 341-358, 2024.
- [9] S. Gopalakrishnan, R. Rajasekar, and M. Amarnath, "Shape memory alloy reinforced polymer composites: Damping and impact resistance," *Compos. Struct.*, vol. 285, 2022.
- [10] F. Kong, Y. Zhao, and J. Liu, "Effect of annealing and pre-deformation on superelastic behavior of NiTi wires," *Mater. Sci. Eng. A*, vol. 891, 2024.
- [11] G. S. Bigelow, S. A. Padula, A. Garg, D. Gaydosch, and R. D. Noebe, "Characterization of ternary NiTiHf high-temperature shape memory alloys," *Metall. Mater. Trans. A*, vol. 53, pp. 3103-3119, 2022.
- [12] S. Santosh, T. Sampath Kumar, M. Nithyadharan, V. Pandian, and G. Rajyalakshmi, "Effect of silicon addition on transformation temperatures and microstructure of NiTi shape memory alloy," *Mater. Today Proc.*, vol. 92, pp. 234-240, 2024.
- [13] Y. Liu, Z. Xie, J. Van Humbeeck, and L. Delaey, "Asymmetry of stress-strain curves under tension and compression for NiTi shape memory alloys," *Acta Mater.*, vol. 46, pp. 4325-4338, 2005.
- [14] H. Ito, T. Omori, Y. Sutou, and R. Kainuma, "Martensitic transformation and shape memory effect in Mn-rich Cu-Mn-Al alloys," *Mater. Trans.*, vol. 66, pp. 45-52, 2025.
- [15] O. Fakhraei, M. Malekan, and M. H. Fathi, "Effect of aluminum content on thermal and mechanical properties of Cu-Al-Fe shape memory alloys," *Trans. Nonferrous Met. Soc. China*, vol. 30, pp. 440-451, 2020.
- [16] S. N. Saud, E. Hamzah, T. Abubakar, and M. Bakhsheshi-Rad, "Influence of Ta additions on the microstructure and shape memory properties of Cu-Al-Ni shape memory alloys," *J. Therm. Anal. Calorim.*, vol. 131, pp. 1421-1432, 2017.
- [17] Kulkarni, R. Singh, and P. Sharma, "Corrosion behavior of Fe-based shape memory alloys for civil engineering applications," *Constr. Build. Mater.*, vol. 371, 2025.
- [18] K. J. Lim, H. S. Kim, and J. W. Yeh, "Transformation characteristics of CrMnFeCoNi high-entropy shape memory alloys," *Scr. Mater.*, vol. 241, 2025.
- [19] Haldar, S. Suresh, and A. A. Bhattacharya, "Phonon softening in Ni-Mn-Ga magnetic shape memory alloys," *Appl. Phys. Lett.*, vol. 99, 2011.
- [20] M. Tabrizikahou, M. Kuczma, P. Nowotarski, M. Kwiatek, and A. Javanmardi, "Sustainability of civil structures through the application of smart materials: A review," *Materials*, vol. 14, 2024.

- [21] R. Velázquez, E. E. Pissaloux, M. Hafez, and J. Szewczyk, "Tactile rendering with shape-memory-alloy pin-matrix," *IEEE Trans. Instrum. Meas.*, vol. 57, pp. 1051-1057, 2007.
- [22] C. A. Biffi, P. Bassani, A. Tuissi, and F. Passaretti, "Microstructural and mechanical response of NiTi lattice 3D structure produced by selective laser melting," *Metals*, vol. 10, 2016.
- [23] J. H. Roh, "Thermomechanical modeling of shape memory alloys considering strain-rate effects," *Smart Mater. Struct.*, vol. 23, 2014.
- [24] R. Simoes, S. Kyriakides, and E. Shaw, "Fatigue crack propagation in NiTi shape memory alloys," *Int. J. Fatigue*, vol. 157, 2022.
- [25] R. J. Immanuel, S. C. Panigrahi, G. Rajamurugan, S. Nayak, and S. K. Sahu, "Challenges in the machining of shape memory alloys: A review," *Mater. Today Proc.*, vol. 62, pp. 4502-4509, 2022.
- [26] M. K. Khorramabadi and J. Rezaeepazhand, "Adaptive vibration control of shape memory alloy beam," *J. Intell. Mater. Syst. Struct.*, vol. 33, pp. 1562-1574, 2022.
- [27] P. Shayanfard, A. Heckmann, and K. Dreßler, "Phase-field simulation of fatigue crack growth in NiTi shape memory alloys," *Eng. Fract. Mech.*, vol. 267, 2022.



IJOER
ENGINEERING JOURNAL

International Journal of Engineering Research and Science



Published by
AD Publications

Contact us



+91-7665235235



www.ijoer.com



info@ijoer.com